Graphitic-C_3N_4 coated floating glass beads for photocatalytic destruction of synthetic and natural organic compounds in water under UV light

Jianing Hui [a*], Carlos J. Pestana [b], Marine Caux [a], H. Q. Nimal Gunaratne [c], Christine Edwards [b], Peter K. J. Robertson [c], Linda A. Lawton [b] and John T. S. Irvine [a*]

[a] School of Chemistry, University of St Andrews, North Haugh, St Andrews, Scotland, KY16 9ST, UK.

[b] School of Pharmacy and Life Sciences, Robert Gordon University, Garthdee Road, Aberdeen, Scotland, AB10 7GJ, UK.

[c] School of Chemistry and Chemical Engineering, the Queen's University of Belfast, Steanmillis Road, Belfast, Northern Ireland, BT9 5AG, UK.

Keywords: *g*-C_3N_4, Floating photocatalysts, Microcystin-LR, Cylindrospermopsin, Dye degradation

Abstract:

Many drinking water reservoirs can contain organic pollutants such as artificial synthesized dye and drugs. On the other hand, some naturally occurring microorganisms such as cyanobacteria, are capable of producing toxic secondary metabolites (cyanotoxins) causing detrimental health effects in humans and animals are also present in water reservoirs. Photocatalytic destruction of organic pollutants in-reservoir requires not only good photo-catalytically activity but also efficacy of distribution and recycling. We report here, a facile calcination method of coating graphitic carbon nitride (*g*-C_3N_4) onto porous glass beads. Influences of precursor and heating temperature on photocatalytic activity were evaluated by photocatalytic degradation of methyl orange. The yellow floating beads show comparable activity to P25 (TiO_2) coated beads in the removal of two of the most frequently occurring cyanobacterial toxins, microcystin-LR and cylindrospermopsin, in artificial freshwater under UV light irradiation. Microcystin-LR was destroyed within 60 min and cylindrospermopsin was removed after 100 min UV irradiation. The coated *g*-C_3N_4 layer is very robust and shows negligible degradation on photocatalytic

performance when recycled. The recycling of the photocatalyst is very simple because of the large size of the catalyst-coated beads. A large batch was successfully produced in a lab tube furnace. For further application, the ability of *g*-C_3N_4 absorbing visible light could pave the way to utilise sunlight for the destruction of toxins in the water.

1. Introduction

Drinking water contamination caused by organic pollutants has been a worldwide concern. Synthetic pollutants that created as a result of human activity are easy to control by cutting off the pollution sources, while some organic compounds generated in nature are more complicated to deal with. Cyanotoxins due to algae blooms is one of the major threat to the safety of drinking water, especially in some developing countries.[1] A large number of studies have been carried out on cyanobacterial toxin monitoring and management. Microcystin-LR (MC-LR) and cylindrospermopsin (CYL) are two of the most commonly occurring toxins found in reservoir water.[2] MC-LR, a member of a group containing over 240 congeners, is a cyclic heptapeptide with two variable amino acid residue positions (see Fig. S1a). MC-LR has been reported in many lakes/reservoirs that provide drinking water, negatively affecting water quality. CYL is a polycyclic uracil derivative which contains both guanidino and sulphate moieties (see Fig. S1b).[3] Both toxins are known to be relatively stable compounds, which makes them difficult to remove by conventional treatment methods when dissolved in the raw water.

Photocatalytic destruction is a promising technology to remove cyanotoxins within the reservoir using solar energy directly.[4] On the surface of a semiconductor photocatalyst, hydroxide ions are oxidised to hydroxyl radicals ($OH^{\cdot}$) at the valence band (VB). The photogenerated $OH^{\cdot}$ radicals can oxidize a broad range of organic pollutants. Oxygen is reduced to superoxide radical anions ($O_2^{\cdot -}$) at the conduction band (CB). The $O_2^{\cdot -}$ anions may be protonated ultimately forming hydrogen peroxides (H_2O_2), both of which are also oxidizing agents.[5, 6]

Graphitic carbon nitride (*g*-C_3N_4) is a metal-free semiconductor, possessing carbon and nitrogen atoms arranged based on a tri-s-triazine unit.[7, 8] The ideal *g*-C_3N_4 is constructed from highly conjugated two-dimensional sheets with a graphic structure in three-dimension. Because of the good thermal-, chemical-, and photostability of this material, as well as favourable band

positions [CB = − 1.4 V, VB = 1.3 V vs. Ag/AgCl at pH 6.6], *g*-C_3N_4 is suitable for visible-light-driven water splitting and dye degradation.[9-11] There have been some investigations on the photocatalytic destruction of cyanobacterial toxins over the past few years.[12-16] Only a few studies were about *g*-C_3N_4. Xu et al.[16] reported *g*-C_3N_4/$BiVO_4$, a Z-scheme heterojunction, removed MC-LR efficiently under visible light using photo-generated hydroxyl radicals and superoxide radicals. However, the effect of a single *g*-C_3N_4 photocatalyst (i.e. without invoking composite systems incorporating toxic metals) in cyanobacterial toxins destruction has not been studied yet.

One of the major drawbacks to the wide application of photocatalyst in real water such as reservoirs and rivers is the size of the photocatalyst. Most of the reported high activity photocatalysts are in the size of micrometres or even nanometres. The direct use of this kind of fine powders in water has potential danger to the environment.[17, 18] Moreover, most of these photocatalysts have a higher density than water, which means they will accumulate at the bottom of the reservoir in the absence of agitation. As light penetration is limited to the upper part of the water column obtaining light irradiation for these photocatalytic nanoparticles is problematic. One of the most promising strategies is to immobilize the active photocatalysts onto a floating substrate.[19] Different types of substrates such as expanded perlite[14, 15, 20], fly ash beads[21] and expanded polymer spheres[22] have been used as photocatalysts substrates, however, these substrates have inherent disadvantages. For example, expanded perlite is very fragile because of its thin-walled structure. Coal fly ash is usually in micro-metre size, which is difficult to recover. The polymer substrates are also susceptible to degradation under UV light irradiation. Moreover, less stable substrates will further result in catalyst shedding during usage. Jingke Song et al. [14, 15] reported effective inactivation of *Microcystis aeruginosa* (toxic cyanobacterium) using C_3N_4 and C_3N_4/TiO_2 immobilized on expanded perlite, however, the photocatalysts showed an obvious shedding after a non-stirring test.

In this work, we used expanded glass beads with a porous inner core but relative dense shell structure for *g*-C_3N_4 loading. These cheap glass beads are obtained during waste glass recycling and used as a lightweight building material. They present with good robustness and relatively regular surface for photocatalysts coating. A facile calcination method using a polymer precursor was used to obtain a *g*-C_3N_4 coating layer. Optimization on coating process was

carried out and the photocatalytic activity of obtained yellow floating photocatalysts was evaluated in dye degradation. To compare with the commercial TiO_2 (P25), P25 coated glass beads were prepared as a reference in the cyanobacterial toxin removal test.

2. Experimental

2.1 Materials and chemicals

Expanded glass beads (Diameter: 2~4 mm) were provided by Dennert Poraver GmbH (Germany). P25 (TiO_2, Rutile: Anatase/ 85: 15, 99.9%, 20 nm, from Aeroxide), thiourea (Sigma Aldrich, >99%), dicyandiamide (Sigma Aldrich, 99%), melamine (Sigma Aldrich, 99%) and ethylenediaminetetraacetic acid (EDTA, Sigma Aldrich, ACS reagent) were used as received. Isopropanol (2-propanol, ACS, 99.5%) was obtained from Alfa Aesar. Deionized (DI) water was used in all the experiment. MC-LR was obtained as per Edwards et al.[23], CYL was obtained from Enzo Life Science, USA. Artificial freshwater was prepared according to Akkanen and Kokkonen[24], in short $CaCl_2$ (58.8 mg L^{-1}), $MgSO_4$ (24.7 mg L^{-1}), $NaHCO_3$ (13.0 mg L^{-1}), and KCl (1.2 mg L^{-1}) were dissolved in ultrapure water (18.2 MΩ) and the pH adjusted to 7 with either HCl or NaOH (all chemicals were acquired from Fisher Scientific, UK).

2.2 Preparation of *g*-C_3N_4 coated glass beads

Glass beads (used as received) were washed in an ultrasonic bath (Ultrawave U300H, SLS, UK) to remove any potential surface contamination with acetone and DI water, respectively. Clean beads were dried in an oven at 80 °C for further coating. For *g*-C_3N_4 coating, wet beads (3 g) were mixed with the precursor (1.2 g) thoroughly to let the powder adhere to the surface of the bead. After that, the mixture was transferred into a custom-made aluminium crucible and covered with aluminium foil. The aluminium crucible was calcined in a muffle furnace at a temperature range from 450 to 600 °C. Post calcination the *g*-C_3N_4 coated beads were agitated gently in a stainless-steel sieve (pore size 1 mm) and washed with water thoroughly to remove unattached *g*-C_3N_4 particles. The loading amount is between 10 wt% and 15 wt% depending on different heating processes.

121 2.3 Preparation of P25 coated glass beads

122 The same pre-treatment as described for *g*-C_3N_4 coated glass beads was performed before
123 coating with P25. The precursor turbid liquid was prepared by adding 1 g P25 nano-powder
124 into 10 mL water. An ultrasonic bath was employed to break agglomeration and form a
125 homogeneous suspension. Pre-treated glass beads were immersed into the precursor turbid
126 liquid for 10 min with intermittent stirring. After this, the beads were removed from the
127 precursor solution and dried in an oven at 80 °C. Coated beads were calcined at 550 °C to create
128 a strong bonding between TiO_2 and the glass beads. Each cycle of coating deposited about 2
129 wt% TiO_2 catalyst. Repeated coatings were carried out to achieve a catalyst loading amount of
130 more than 12 wt%. The beads used in the present work present with a TiO_2 loading of
131 approximately 12 wt%. Photos in Fig. S2 show 100 g batch achieved in a lab tube furnace with
132 a uniform coating of *g*-C_3N_4 and P25.
133
134 2.4 Characterization

135 The morphologies and elemental distribution analysis of coated glass beads were carried
136 out on a scanning electron microscope (SEM, FEI Scios DualBeam) and its dispersive X-ray
137 spectroscopy (EDX) module. The phase was confirmed by powder X-ray diffraction (XRD) on
138 a PANalytical Empyrean X-ray diffractometer operated in reflection mode (Cu Kα1). Glass
139 beads were ground to a powder using a pestle and mortar before performing XRD analysis. UV-
140 Vis absorbance spectra were collected on an ultraviolet-visible spectrophotometer (JASCO-
141 V550). The BET (Brunauer-Emmett-Teller) surface area of samples was tested on a
142 Micrometrics TriStarII 3020 instrument.
143
144 2.5 Catalyst evaluation by photocatalytic dye degradation

145 To optimize the *g*-C_3N_4 coating process on glass beads, a custom-made multi-channels
146 photoreactor was employed to run photocatalytic dye degradation experiments. As shown in
147 Fig. S3a, a maximum of eight glass vial can be held in this reactor by a glass vial holder. A Fe
148 doped metal halide lamp (250 W) was fixed 15 cm above the vial holder. To allow the same
149 amount of light irradiation for each sample, a DC gear motor was used to rotate vial holder
150 gently at a speed of 10 rpm. Cooling fans were fixed beside glass vials to maintain the

temperature at 25 °C during the reaction. Each glass vial was covered by a thin quartz glass window to prevent water evaporation. For methyl orange (MO) degradation, each glass vial was filled with 25 mL 6.5 $mg \cdot mL^{-1}$ (0.02 mM) MO aqueous solution. The quenchers (isopropanol, ethylenediaminetetraacetic acid) were added by a volume ratio 1:100 to the solution. Samples (500 μL) were withdrawn and analysed for dye concentration by UV-VIS absorbance at predetermined time intervals. The output spectra of metal halide lamp without and with UV cut-off filter (>400 nm) were presented in Fig. S3b and 3c.

2.6 Photocatalytic cyanotoxins destruction

Photocatalytic degradation of selected cyanobacterial toxins was carried out in a custom-build photo-reactor. Four non-integrated fluorescent lamps (36 W each, Philips) were used as UV light sources, as shown in Fig. S4a. 300 mg coated beads were suspended in 10 mL artificial freshwater with a toxin concentration of 10 $\mu g \cdot mL^{-1}$. Magnetic stirring was applied to provide better diffusion. The temperature of the reactor was maintained at 25 °C by using cooling fans. Samples (200 μL) were withdrawn and analysed for remaining MC-LR by HPLC-PDA and remaining CYL by UPLC-PDA at predetermined time intervals. The output spectrum of the fluorescent lamp can be found in Fig. S4b.

2.7 HPLC analysis of MC-LR and CYL

HPLC analysis was performed on a Waters 2695 Separation Module. High-resolution photodiode array detection was performed with a Waters 2996 Photodiode Array Detector (PDA). Analysis of microcystin-LR was performed with a Symmetry C18 column 2.1 mm (inner diameter) x 150 mm with a 5 μm particle size (all Waters, UK). The mobile phases used were ultrapure water (18.2 MΩ) and acetonitrile (Fisher Scientific, UK), both containing 0.05% trifluoroacetic acid (Fisher Scientific, UK). Chromatography was achieved with a linear gradient from 15 to 75% acetonitrile over 10 min, followed by a solvent wash and equilibration. The column temperature was set to 40 °C and the flowrate applied was 0.3 mL min^{-1}. Injection volume was 25 μL. Analysis of cylindrospermopsin was performed using a reverse-phase Atlantis dC18 column 2.1 mm (inner diameter) x 150 mm with a 5 μm particle size (Waters UK). Acquity UPLC System with Xevo quadrupole time of flight (QTOF) mass spectrometry

in series (Waters, Elstree, UK) The mobile phases used were ultrapure water (18.2 MΩ) and methanol (Fisher Scientific, UK). Chromatography was achieved with a linear gradient from 2 to 10 % methanol over 10 min, followed by a solvent wash and equilibration. The column temperature was set to 40 °C and the flow rate applied was 0.3 mL min^{-1}. The resolution of the PDA was set to 1.2 nm and data was acquired over a range of 200 to 400 nm for both analytes.

3. Results and discussion

3.1 Precursors for producing *g*-C_3N_4

Three precursors thiourea (CH_4N_2S), dicyandiamide ($C_2H_4N_4$) and melamine ($C_3H_6N_6$), with increasing carbon content, were used for *g*-C_3N_4 coating. Based on previous studies on powder C_3N_4 synthesis, the formation of C_3N_4 from single carbon precursors such as urea and thiourea usually follows a continuous polymerization process with intermediate products of $C_2H_4N_4$ and $C_3H_6N_6$. The precursors sublime during the heating process and condense when forming a tri-s-triazine structure. The sublimation of the precursor or any intermediate products allows the C_3N_4 to be coated onto the glass beads substrates.

Calcination of glass beads with thiourea, dicyandiamide and melamine at 500 °C for 5 h, yielded coated C_3N_4 beads with loadings of 0.7%, 9.8% and 14.3%, respectively. Both dicyandiamide and melamine created a light-yellow coating layer upon glass beads. The glass beads calcined with thiourea showed no visible colour change. This could be expected, as thiourea, with the simplest structure, has much less chance to form polymer structure before decomposing in air. The morphologies of the coated glass beads using dicyandiamide and melamine were characterized by SEM, as shown in Fig. S5. Coating layers with rough surfaces were found on both samples. The coating layer prepared with melamine looked more porous than the one produced from dicyandiamide. Moreover, the holes on the glass beads were filled by polymer after coating indicating massive condensation during melamine sublimation.

X-ray powder diffraction was employed to check the crystal structure of the formed coating layer. The coated beads were ground into fine powder by mortar and pestle before analysis. A weak reflection peak at 27.6° was determined in *g*-C_3N_4 coated beads with both precursors (Fig. 1a). It is indexed as (002) corresponding to the aromatic stack plane.[7, 25] The sample prepared by melamine showed a higher peak intensity. This indicated a more crystalline

structure. Moreover, the peak shifted to a higher angle, therefore, lower d spacing, which suggested tighter packing of the 2D tri-s-triazine sheets. The amorphous glass beads showed a broad bump at the low angle region. Only a small reflection peak at 26.7° was observed. More than six impurity elements in the recycled glass beads were detected. It was difficult to identify these due to the low peak intensity.

The absorbance properties of the yellow beads after coating were characterized by UV-VIS diffuse reflectance spectroscopy (Fig. 1b). Almost the same absorbance curve was found in two different precursor coated samples, with a calculated bandgap around 2.65 eV. This is close to the pure *g*-C_3N_4 reference material (2.66 eV). The same light absorption region compared to powdered *g*-C_3N_4 is expected in the photocatalysis test.

FTIR spectra revealed the chemical structure of coated *g*-C_3N_4, as shown in Fig, 1c. A small broad bump at the 3000-3500 cm^{-1} region was attributed to the N-H and O-H stretches from free amino groups and hydroxyl species. The strong band from 1200 to 1700 cm^{-1} resulted from stretching and vibration of C-N and C-N-C bonds.[26] Another sharp band observed at 806 cm^{-1} was attributed to the breathing mode of tri-s-triazine structure.[27]

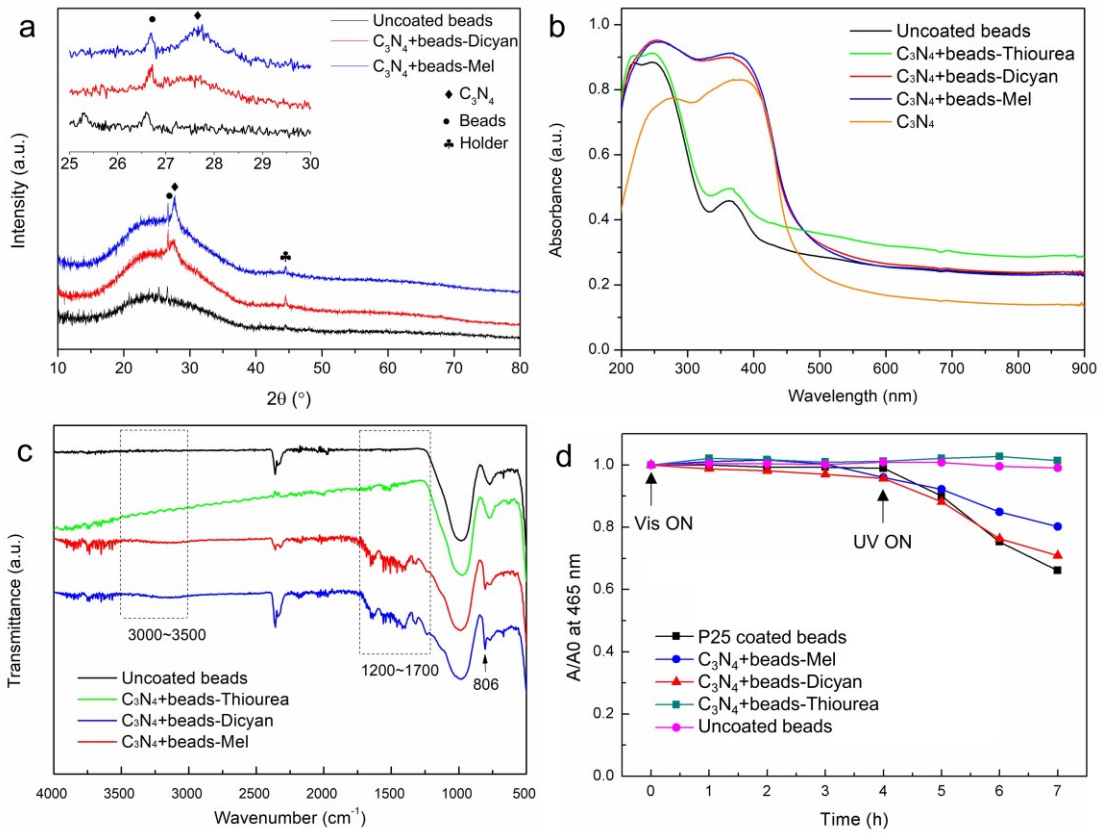

Figure 1. (a) X-ray diffraction pattern of uncoated and *g*-C_3N_4 coated beads. Insert is the detail of *g*-C_3N_4(002) peak; (b) UV-VIS diffuse reflectance spectra of uncoated and *g*-C_3N_4 coated beads. Powder *g*-C_3N_4 was added as a reference; (c) FTIR specta of uncoated and *g*-C_3N_4 coated beads; (d) Normalized absorption intensity at 465 nm in methyl orange degradation using different coated beads. UVCUT 400 was removed after 4 h. Samples were calcinated for 5 h at 500 °C.

All the characterizations performed confirmed the successful coating of *g*-C_3N_4 on expanded glass beads surface *via* simple calcination. The as-prepared yellow beads were used for methyl orange degradation to evaluate the photocatalytic activity. P25 coated beads were employed as a reference sample. As shown in Fig. 1d, all the samples exhibited poor photocatalytic activity under visible light ($\lambda \geq 400$ nm). Only melamine coated beads started to show dye degradation after 4 h irradiation. When switched to UV light ($\lambda \geq 250$ nm), beads coated with P25 and *g*-C_3N_4 showed activity for methyl orange removal. P25 coated beads had the best performance, followed by *g*-C_3N_4 coated beads prepared via dicyandiamide. *g*-C_3N_4 coated beads prepared with melamine showed moderate performance, while the beads prepared with thiourea showed no activity compared to uncoated beads. One possible reason for the poor activity of *g*-C_3N_4 coated beads under visible light is low light absorption. The UV-Vis absorbance curve shows coated beads have an absorption edge around 460 nm, however, the maximum absorption appears until 370 nm. This means when using a UV cut filter (≥ 400 nm), the light-harvesting on the *g*-C_3N_4 surface is much lower than when not using a filter. A 20% decrease of relative light intensity was also determined when checking the output spectrum with the spectrometer, which is another factor that causes low activity under visible light.

Although the dicyandiamide prepared *g*-C_3N_4 coating layer showed better dye degradation performance under UV light, more shedding of the photocatalyst from the glass beads into the solution was observed during the test under continuous stirring. Considering the high yield and mechanical stability, melamine seems to be a better precursor for *g*-C_3N_4 coating onto expanded glass beads.

3.2 Influence of calcination temperature

In our previous study, we found the calcination temperature in bulk *g*-C_3N_4 synthesis had a significant influence on photocatalytic performance by affecting the crystal structure and electronic structure of *g*-C_3N_4. Therefore, the calcination temperature for *g*-C_3N_4 coating was also optimized in this work.[25] Samples were prepared at 450 to 600 °C for 5 h with the same amount of melamine.

As shown in Fig. 2a, the peak intensity at (002) increased when the temperature rose from 450 °C to 500 °C. An obvious peak shift to a higher angle in terms of lower d spacing was observed at 500 °C. Both indicated improved crystallization with tighter packed 2D polymer sheets. When the temperature reached 550 °C, the peak intensity decreased, which may be because the polymer structure started to decompose after 500 °C. This was confirmed by thermogravimetric analysis (TGA) when heating bulk *g*-C_3N_4 in air, as shown in Fig. S6. Due to this thermal decomposition, no reflection peak of *g*-C_3N_4 was detected in samples prepared at 600 °C, which meant most of the coated *g*-C_3N_4 was burned off. The surface morphologies of these coated glass beads characterized by SEM showed this change in Fig. S7.

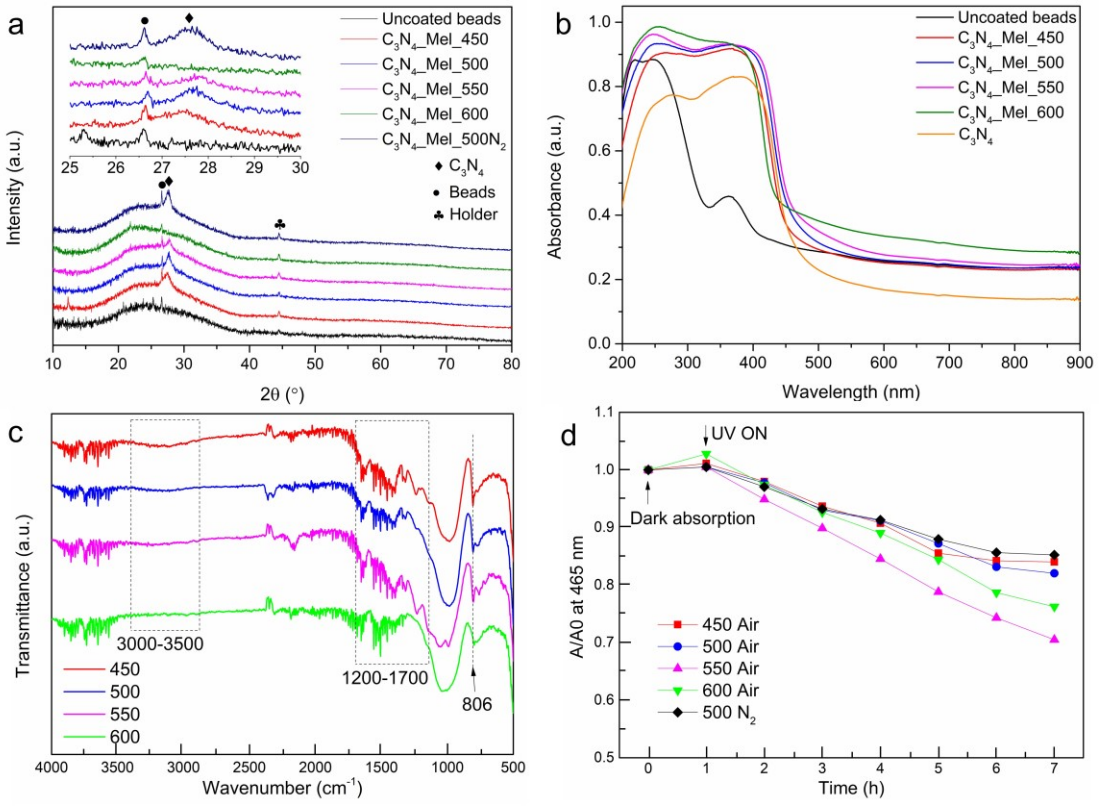

Figure 2. (a) X-ray diffraction pattern of uncoated and *g*-C_3N_4 coated beads using melamine at different temperatures. Insert is the detail of *g*-C_3N_4(002) peak; (b) UV-VIS diffuse reflectance

spectra of uncoated and *g*-C_3N_4 coated beads at different temperatures. Powder *g*-C_3N_4 was added as a reference; (c) FTIR spectra of *g*-C_3N_4 coated beads at different temperatures; (d) Normalized absorption intensity at 465 nm in methyl orange degradation using coated beads prepared at different temperatures. UV light was switched on after 1 h dark absorption.

UV-Vis absorbance of coated beads presented a redshift as temperature increased from 450 °C to 550 °C (Fig. 2b). This suggested that a high annealing temperature is beneficial to form the crystalline structure of *g*-C_3N_4, though parts of the polymer had been decomposed at 550 °C. The sample prepared at 600 °C showed a blue shift as the decomposition domains and left little active material. Similar details were observed in the FTIR spectra in Fig. 2c. The sharp band at 806 cm^{-1} attributed to tri-s-triazine breathing mode showed the highest intensity at 550 °C and almost disappeared at 600 °C.

Methyl orange degradation was carried out to evaluate the photocatalytic performance of coated beads. As shown in Fig. 2d, the sample prepared at 550 °C showed the highest activity under UV light. It is surprising here that the sample calcined at 600 °C showed better performance than the beads prepared at a lower temperature (450 and 500 °C) though much less of the *g*-C_3N_4 remained. This suggests the amount of active material may not be a key factor for photocatalytic activity because the reaction only occurs at the surface with incident light irradiation. A sample prepared in an N_2 atmosphere at 500 °C was used for comparison here to elucidate the influence of the gas atmosphere. No obvious difference from a sample prepared in the air at the same temperature was observed. Good recycling performance was found when using *g*-C_3N_4 coated glass beads prepared at 550 °C for methyl orange degradation, as shown in Fig. S8.

3.3 Catalysts distribution on glass beads

EDS mapping was employed to check the elemental distribution on coated glass beads. *g*-C_3N_4 coated beads presented uniform distribution of the N element layer on the top surface, as shown in Fig. 3c. Moreover, the N signal was detected inside the bulk of the beads. This revealed that intermediate products generated during *g*-C_3N_4 formation diffused through the pores and condensed. This was a major difference to P25 coated glass beads in regard to active

material distribution. Most of the coated P25 was located on the glass beads surface, as shown in Fig. S9. A thin layer containing Ti and O distributed uniformly on glass beads surface. XRD and UV-VIS absorbance confirmed the existence of the TiO_2 phase. The backbone of the porous beads mainly contained Na, Si, Ca and O, as shown in both P25 and *g*-C_3N_4 coated beads.

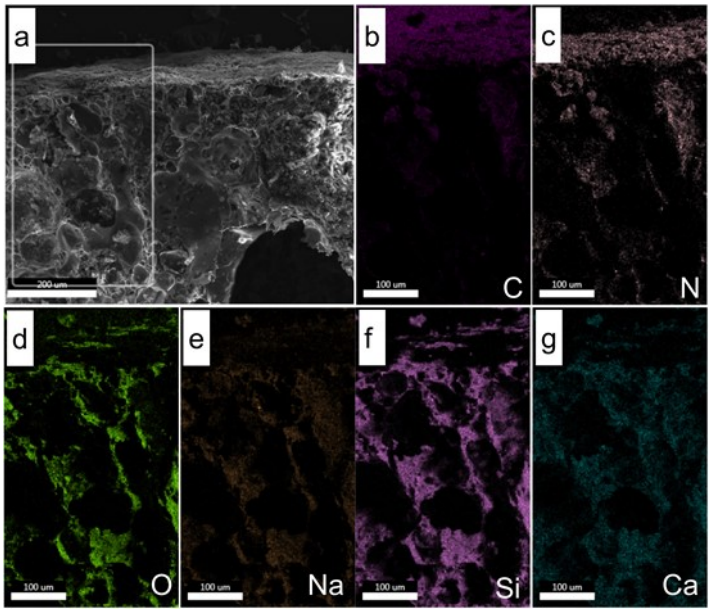

Figure 3. EDS mapping of *g*-C_3N_4 coated glass beads at a cross-section. The sample was prepared with melamine at 550 °C, 5 h. Scale bar is 200 μm in (a) and 100 μm in (b-g).

3.4 Photocatalytic removal of cyanobacterial toxins

The results obtained from both photocatalysts in the decomposition reaction of MC-LR and CYL are summarised in Fig. 4. In both cases, the coated beads were immersed in the solution containing the toxin for ten minutes in the dark for equilibration and allowing for dark absorption, before the commencement of irradiation. Controls are presented in the supplementary information. The *g*-C_3N_4 coated beads used in this experiment were prepared at 550 C, with loading content around 12% wt. This is almost the same amount of loading of the P25 coated glass beads. The BET surface area of *g*-C_3N_4 and P25 coated beads are 2.3 $m^2\ g^{-1}$ and 2.6 $m^2\ g^{-1}$, respectively. The N_2 adsorption-desorption isotherms were presented in Fig. S10.

In the MC-LR removal experiment, both coated beads showed about 5% toxin adsorption in dark. The reaction profiles after turning on UV light showed *g*-C_3N_4 coated beads resulted in the complete removal of MC-LR 15 min earlier than the case with P25 coated beads. Control experiments in Fig. S11 showed neither catalysts in dark solution nor toxin solution in light

without catalyst had any evidence of decomposition of the toxins.

In the case of CYL, a big difference in dark absorption was observed in the initial 10 min before photocatalysis. P25 coated beads absorbed 25% CYL while *g*-C_3N_4 coated beads absorbed 5% of the compound. The total time used for full removal of toxins was the same, which suggested the *g*-C_3N_4 coated beads had a better photocatalytic efficiency compared to the P25 coated materials for CYL removal. Again, light control and dark control experiments were carried out, with both showing no CYL removal in Fig. S12.

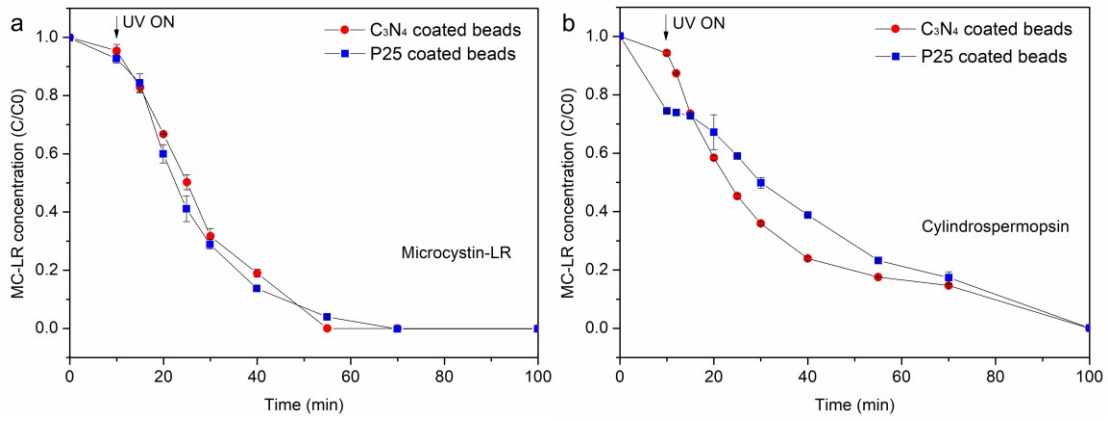

Figure 4. Graph showing the progress of photo-decomposition reactions of microcystin-LR (a) and cylindrospermopsin (b) with TiO_2 and *g*-C_3N_4 carried out at 25 °C in an open photoreactor. g-C_3N_4 coated glass beads in this experiment were prepared with melamine at 550 °C, 5 h.

CYL is structurally very different to MC-LR lacking in any carboxylic acid groups and an oligopeptide macrocyclic structure. Due to the presence of a pendant strongly basic guanidine functionality in MC-LR, it is expected to abstract a proton from one carboxylic acid to form a zwitterion while leaving the second carboxylic acid group 'unionised'. It is well known that carboxylic acid groups have a binding affinity towards TiO_2, thereby, making the photocatalytic process more feasible. Even without such binding functionalities CYL still underwent efficient photodecomposition with both photocatalysts. The kinetic profiles for the destruction of both toxins bore similarities despite the structural differences. It should be stressed that the absorption behaviour of CYL on the surface of *g*-C_3N_4 is less well understood than MC-LR. Nevertheless, the photocatalytic performance of *g*-C_3N_4 in the destruction process for both

toxins used in this study was comparable to TiO_2.

The weight of the catalysts was monitored before and after the test. When applying moderate stirring during the test, no obvious shedding was observed. A limited amount of *g*-C_3N_4 shedding was, however, still found when stirring vigorously or using an ultrasonic bath. The TEM images in Fig. S13 show different shapes of *g*-C_3N_4 shedding. EDS confirmed the composition are mainly C and N. Nevertheless, shedding contamination can be avoided by washing the catalysts thoroughly to remove loose-packed active materials before use.

3.5 Mechanism discussion

Although *g*-C_3N_4 coated glass beads have comparable performance to P25 coated ones, the mechanism for toxin removal and dye degradation are different. The photocatalytic removal of cyanobacterial toxins by TiO_2 photocatalysts has been studied previously.[28-30] The photogenerated hole at the valence band reacts with water to form hydroxyl radicals ($OH^{\cdot}$), which have very high oxidation overpotential thus has the capacity of oxidizing a variety of organic pollutants. For *g*-C_3N_4, the valence band is located negative to the $OH^{\cdot}/H_2O$ redox potential therefore unable to generate $OH^{\cdot}$. Only superoxide radical anions ($O_2^{\cdot -}$) can be generated at the conduction band. The $O_2^{\cdot -}$ may subsequently react with protons (H^+) to create H_2O_2. The generated H_2O_2 could be the source of hydroxyl radicals ($OH^{\cdot}$). The processes to form $OH^{\cdot}$ have been illustrated in Fig. 5 and Eq. (1-4).

$$O_2 + e^- \rightarrow O_2^{\cdot -} \quad (1)$$

$$O_2^{\cdot -} + H^+ \rightarrow HO_2^{\cdot} \quad (2)$$

$$HO_2^{\cdot} + e^- + H^+ \rightarrow H_2O_2 \quad (3)$$

$$H_2O_2 + e^- \rightarrow OH^{\cdot} + OH^- \quad (4)$$

The $OH^{\cdot}$, with a largeoxidation overpotential, is believed to be the main radical that oxidizes organic pollutants during photocatalysis, though both $O_2^{\cdot -}$ and $HO_2^{\cdot}$ are reactive. A comparison experiment was carried out using different quenchers in methyl orange degradation. As shown in Fig. S14, the addition of isopropanol, a $OH^{\cdot}$ quencher resulted in a reduction of photocatalyst performance. This indicated $OH^{\cdot}$ is essential to the degradation reaction. The addition of EDTA, a hole quencher improved the activity. This is because hole scavenger at the valence band inhibits electron-hole recombination. EDTA also introduced protons, which

promoted the reaction to create $HO_2^{\cdot}$ and H_2O_2, thus a significant performance increase was observed.

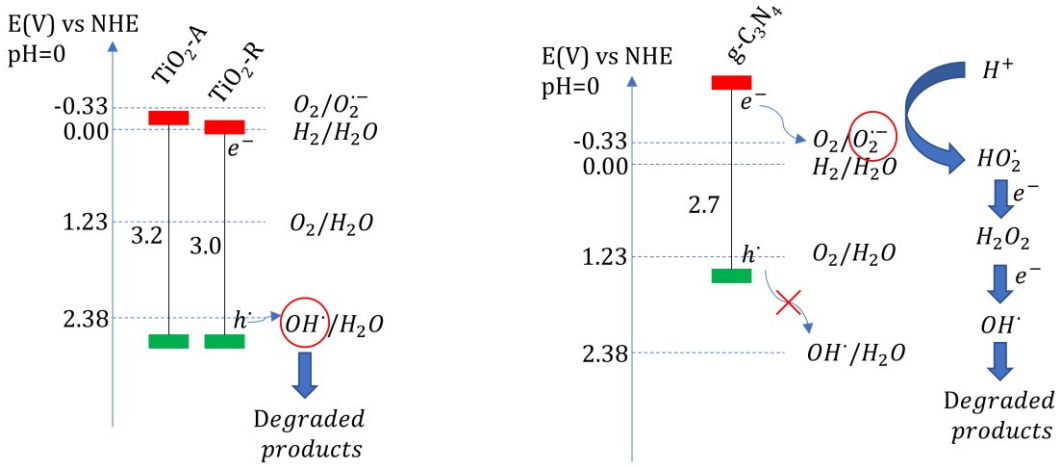

Figure 5. Proposed different mechanisms for toxin degradation in P25 and *g*-C_3N_4 coated glass beads.

4. Conclusions

We have demonstrated, here, the comparable performance of a simple *g*-C_3N_4 photocatalyst coated on floating expanded glass beads in comparison to traditional TiO_2 (P25) photocatalyst for photo-removal of MC-LR and CYL from water. It must be stressed this simple *g*-C_3N_4 is devoid of any detrimental metals and their insolubility in water makes it attractive materials for water purification. The floating material made recovery of the photocatalysts relatively easy which would allow for subsequent reuse. Moreover, the facile preparation process enables large batch production for full-scale application.

Acknowledgements

We acknowledge the funding provided by the Engineering and Physical Sciences Research Council, UK (Global Challenge Research Fund: EP/P029280/1) towards carrying out this research. We also thank the support on electron microscopes from EPSRC Capital for Great Technologies (Grant EP/LP017008/1 and EP/R02375/1).

References

1. K. Sivonen, in *Encyclopedia of Microbiology (Third Edition)*, ed. M. Schaechter, Academic

Press, Oxford, 2009, DOI: https://doi.org/10.1016/B978-012373944-5.00005-5, pp. 290-307.
2. I. Chorus and J. Bartram, *Toxic Cyanobacteria in Water: A guide to their public health consequences, monitoring and management.* 1999.
3. J. Fastner, R. Heinze, A. R. Humpage, U. Mischke, G. K. Eaglesham and I. Chorus, *Toxicon*, 2003, **42**, 313-321.
4. L. A. Lawton and P. K. J. Robertson, *Chemical Society Reviews*, 1999, **28**, 217-224.
5. M. Pirhashemi, A. Habibi-Yangjeh and S. Rahim Pouran, *J Ind Eng Chem*, 2018, **62**, 1-25.
6. M. Shekofteh-Gohari, A. Habibi-Yangjeh, M. Abitorabi and A. Rouhi, *Critical Reviews in Environmental Science and Technology*, 2018, **48**, 806-857.
7. F. Fina, S. K. Callear, G. M. Carins and J. T. S. Irvine, *Chemistry of Materials*, 2015, **27**, 2612-2618.
8. A. Akhundi, A. Badiei, G. M. Ziarani, A. Habibi-Yangjeh, M. J. Muñoz-Batista and R. Luque, *Mol Catal*, 2020, **488**.
9. X. Wang, K. Maeda, A. Thomas, K. Takanabe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, *Nature Materials*, 2009, **8**, 76-80.
10. S. C. Yan, Z. S. Li and Z. G. Zou, *Langmuir*, 2009, **25**, 10397-10401.
11. Y. Cui, Z. Ding, P. Liu, M. Antonietti, X. Fu and X. Wang, *Physical Chemistry Chemical Physics*, 2012, **14**, 1455-1462.
12. C. Huang, W. Zhang, Z. Yan, J. Gao, W. Liu, P. Tong and L. Zhang, *RSC Advances*, 2015, **5**, 45368-45375.
13. F. Zhang, L. Wang, M. Xiao, F. Liu, X. Xu and E. Du, *Journal of Materials Research*, 2018, **33**, 201-212.
14. J. Song, X. Wang, J. Ma, X. Wang, J. Wang and J. Zhao, *Applied Catalysis B: Environmental*, 2018, **226**, 83-92.
15. J. Song, X. Wang, J. Ma, X. Wang, J. Wang, S. Xia and J. Zhao, *Chem Eng J*, 2018, **348**, 380-388.
16. Y. Xu, B. Hu, J. Liu, K. Tao, R. Wang, Y. Ren, X. Zhao, J. Xu and X. Song, *Journal of the American Ceramic Society*, 2019, **103**, 1281-1292.
17. G. E. Schaumann, A. Philippe, M. Bundschuh, G. Metreveli, S. Klitzke, D. Rakcheev, A. Grun, S. K. Kumahor, M. Kuhn, T. Baumann, F. Lang, W. Manz, R. Schulz and H. J. Vogel, *Sci Total Environ*, 2015, **535**, 3-19.
18. A. Praetorius, M. Scheringer and K. Hungerbuhler, *Environ Sci Technol*, 2012, **46**, 6705-6713.
19. Z. Xing, J. Zhang, J. Cui, J. Yin, T. Zhao, J. Kuang, Z. Xiu, N. Wan and W. Zhou, *Applied Catalysis B: Environmental*, 2018, **225**, 452-467.
20. S. Zhang, H. Li and Z. Yang, *Materials Technology*, 2017, **33**, 1-9.
21. J. Lv, T. Sheng, L. Su, G. Xu, D. Wang, Z. Zheng and Y. Wu, *Applied Surface Science*, 2013, **284**, 229-234.
22. S. Singh, H. Mahalingam and P. K. Singh, *Applied Catalysis A: General*, 2013, **462-463**, 178-195.
23. C. Edwards, L. A. Lawton, S. M. Coyle and P. Ross, *J Chromatogr A*, 1996, **734**, 163-173.
24. J. Akkanen and J. V. K. Kukkonen, *Aquat Toxicol*, 2003, **64**, 53-61.
25. M. Caux, F. Fina, J. T. S. Irvine, H. Idriss and R. Howe, *Catalysis Today*, 2017, **287**, 182-188.
26. X. Yang, F. Qian, G. Zou, M. Li, J. Lu, Y. Li and M. Bao, *Applied Catalysis B: Environmental*, 2016, **193**, 22-35.

27. X. Bai, L. Wang, Y. Wang, W. Yao and Y. Zhu, *Applied Catalysis B: Environmental*, 2014, **152-153**, 262-270.
28. L. A. Lawton, P. K. J. Robertson, B. J. P. A. Cornish, I. L. Marr and M. Jaspars, *Journal of Catalysis*, 2003, **213**, 109-113.
29. C. J. Pestana, C. Edwards, R. Prabhu, P. K. J. Robertson and L. A. Lawton, *J Hazard Mater*, 2015, **300**, 347-353.
30. L. X. Pinho, J. Azevedo, Â. Brito, A. Santos, P. Tamagnini, V. J. P. Vilar, V. M. Vasconcelos and R. A. R. Boaventura, *Chem Eng J*, 2015, **268**, 144-152.